



forest industry
research cooperatives



EUCALYPT COOPERATIVE

Report No. 5

Assessment of the kraft pulp
qualities of *Eucalyptus*
maidenii from two sites aged
5 and 6 years

by

Paul Kibblewhite, John Lloyd, Ruth
McConnochie and Tony Shelbourne

Date: April 2006

SCION 
Next generation biomaterials

Eucalypt Cooperative

Report No. 5

Assessment of the kraft pulp qualities of *Eucalyptus maidenii* from two sites aged 5 and 6 years

By

Paul Kibblewhite, John Lloyd, Ruth
McConnochie and Tony Shelbourne



Eucalypt Cooperative
Report No. 5

**Assessment of the kraft pulp qualities of
Eucalyptus maidenii from two sites aged
5 and 6 years**

By
Paul Kibblewhite, John Lloyd, Ruth
McConnochie and Tony Shelbourne

Date: April 2006
Client: Eucalypt Cooperative

Disclaimer:

The opinions provided in the Report have been prepared for the Client and its specified purposes. Accordingly, any person other than the Client, uses the information in this report entirely at its own risk. The Report has been provided in good faith and on the basis that every endeavour has been made to be accurate and not misleading and to exercise reasonable care, skill and judgment in providing such opinions.

Neither Ensis nor its parent organisations, CSIRO and Scion, or any of its employees, contractors, agents or other persons acting on its behalf or under its control accept any responsibility or liability in respect of any opinion provided in this Report by Ensis.



EXECUTIVE SUMMARY

Kraft fibre and pulp properties of *Eucalyptus maidenii* at age 8- years have been shown to have excellent papermaking properties compared to age 11- years when fibres are of too-high coarseness, have higher refining requirements, and are likely to have poor formation properties. These results suggested that *E. maidenii* fibres at an even younger age may have good kraft pulp qualities. *Eucalyptus maidenii* trees aged 5- and 6-years were therefore sampled. Chip density, pulp yield and pulp fibre properties of the two age groups were similar, except for fibre length. The fibre and pulp properties of the 5-year-old *E. maidenii* sample were equivalent to those of a eucalypt market kraft pulp of superior quality. On the other hand, the shorter length of the fibres in the six-year sample (0.78 mm) compared to that of the five-year sample (0.84 mm) was sufficient to cause a reduction in handsheet bulk below that considered to be acceptable for a eucalypt market kraft pulp, unless a loss of tensile strength can be accepted. The longer fibres of the 5--year-old trees than the 6-year-old may have been due to irrigation of the 5-year-old plantation.

Assessment of the kraft pulp qualities of *Eucalyptus maidenii* from two sites aged 5 and 6 years

By

Paul Kibblewhite, John Lloyd, Ruth McConnochie and Tony Shelbourne

April 2006

INTRODUCTION

Eucalyptus globulus is recognised internationally as the preferred species for the production of short-fibred pulp. New Zealand growers are prevented from planting this species by its susceptibility to fungal disease, insect attack and frosting. Kraft pulp properties of New Zealand-grown *E. nitens* and *E. fastigata* have been shown to be deficient in bulk and of inferior quality compared to *E. globulus* market kraft pulps.

Eucalyptus maidenii at age 8-years had excellent papermaking properties compared to those aged 11-years, when fibres were of too-high coarseness, had higher refining requirements and were likely to have poor formation properties (Kibblewhite *et al.* 2000). The current resource of *E. nitens* is often harvested at a sub-optimal age, when basic wood density is too low, and requires supplementing by resources of older, higher-density wood. Young plantings of *E. maidenii*, less than 5-years old, have recorded wood densities of 450 – 510 kg/m³ and could be pulped as a pure species or used in a mixture with *E. nitens* to produce market kraft pulp.

This study examined the kraft pulp qualities of *E. maidenii* samples from trees aged 5- and 6-years, and compared these with those previously reported for 8- and 11-year-old *E. maidenii* (Kibblewhite *et al.* 2000).

EXPERIMENTAL

Sample origin and history

A 5-year-old stand of *E. maidenii* was selected, located near Waihi. This had been planted on a pasture site with a commercial seedlot from Bolaro Mountain, New South Wales, at 1000 stems per ha, and had been regularly treated with sewerage effluent by sub-surface drip irrigation. This seedlot was

based on seed collected from 56 parent trees. A 6-year-old stand was represented by a provenance trial, located near Kawerau, which had been planted at 950 stems per ha on cleared manuka (*Leptospermum scoparium*) scrubland. This trial has a mix of seven different provenance seedlots, all of which were sampled. At both sites, 40 well-grown trees were measured for diameter at breast height, and pith-to-bark increment cores were collected at that height to determine their wood basic density and to estimate the stand mean. Fifteen trees of similar diameter were then chosen from each site for the pulping study (Table 1), representing the full range of basic density, and equalling the respective observed stand means.

Table 1: Tree diameter and density for the 15-tree samples.

Site/age	Diameter (mm)		Density (kg/m ³)	
	Range	Mean	Range	Mean
Waihi – 5-year-old	177 - 201	191	454 - 566	505
Kawerau – 6 year old	177 - 203	193	443 - 552	501

Log processing and chip sampling

Logs, 7 m long, were cut from the base of each sample tree and then recut into two 3.5-m logs for chipping. The 5- and 6-year-old logs were chipped separately at the TITC sawmill. Each log was chipped individually, oversize and undersize chips were removed and samples of chips collected at regular intervals to represent the whole log. The chip samples from each log were bulked, mixed and a 10- kg sample from each age class removed for kraft pulping.

Chip density

Chip basic density was determined in accordance with Appita method P1s-79, except that the fresh chips were not given the specified soaking period.

Pulping

Chips were pulped, as supplied, to kappa number 20±2 in a 2.0 L pressurised reactor as follows:

- 300 g o.d. chip charge
- 14% effective alkali as Na₂O
- 30% sulphidity
- 4:1 liquor-to-wood ratio
- 90 minutes to maximum temperature
- 160°C maximum temperature

H-factor was varied by varying the pulping time at maximum temperature. Pulp were disintegrated with a propeller stirrer at 1% consistency and screened through a 0.25-mm slotted flat screen. After dewatering and fluffing, kappa number, percentage rejects and total yield were determined. Kappa

numbers for the two *E. maidenii* pulps that were analysed, one from 5-year old and the other from 6-year-old trees, were both 18.7.

Handsheet preparation and evaluation

Handsheets were prepared and pulp physical evaluations made in accordance with Appita standard procedures. The load applied during pulp refining with the PFI mill was 1.77 N/mm. 24-g oven-dried (o.d.) pulp charges were refined at 10 % stock concentration for 500, 1000, 2000 and 4000 revs. Handsheet data are presented on an o.d. basis.

Fibre dimension measurement

Cross-sectional kraft fibre dimensions of thickness, width, wall area and wall thickness were measured using image processing procedures described previously (Figure 1) (Kibblewhite and Bailey 1988). Measurements were made on dried and rewetted fibres reconstituted from kraft handsheets. The product, fibre width \times fibre thickness, is the area of the minimum fibre cross-section-bounding rectangle. The ratio, width/thickness, is an indicator of the collapse potential of the dried and rewetted fibres. The greater the width and the lower the thickness of a fibre cross-section, the greater is the extent of fibre collapse. The relative number of fibres per unit mass of pulp was calculated using the reciprocal of the length \times wall-area product. Length-weighted average fibre lengths were determined with a Metso FiberLab3 instrument using PAPRO standard procedures (Richardson *et al.* 2003).

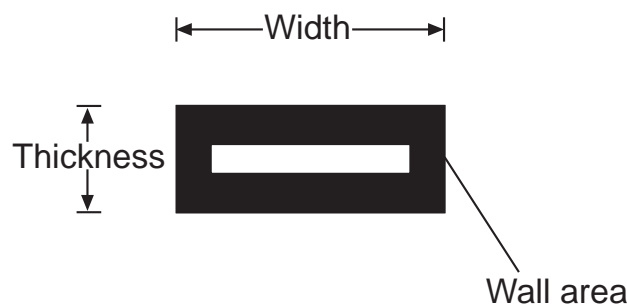


Figure 1: Cross-section diagram of a fibre dried and rewetted from a handsheet.

RESULTS AND DISCUSSION

The 5-year-old *E. maidenii* from Waihi and the 6-year-old trees from Kawerau had very similar chip density, 549 and 554 kg/m³; kraft pulp yields, 53.0 and 52.4%; and wall thickness, both 2.43 μ m (Table 2). Furthermore, delignification rate and chemical consumption were similar for both samples. The fibre length of the 5-year-old material, however, was significantly greater

than that of the 6-year-old, the reverse of what might be expected. Fibre length of the 8- and 11-year-old trees in the earlier study increased strongly with age (Table 2). Relative numbers of fibres and sheet density values are different for the two samples, with the 6-year-old trees being highest. Pulp yields of the 5- and 6-year-old samples were lower by 1-2 % compared to those from older trees (Table 2), as expected (Kibblewhite *et al.* 2000). Cooking chemical requirement was also slightly greater for the 5- and 6- year-old samples.

The pulp fibre dimensions of wall area, wall thickness and perimeter are very similar for the 5- and 6-year-old samples, but lower compared to those of eucalypt pulps considered to be of premium quality, e.g. *E. maidenii* 8- year and *E. globulus* 11-year, (Kibblewhite *et al.* 2000). However, the *E. maidenii* fibres from 5- and 6-year-old trees, while of low wall area, or coarseness, show a resistance to collapse comparable to that of the 8-year *E. maidenii* and 11-year *E. globulus* pulps. Therefore, compared with pulps from the older trees, numbers of fibres are increased with the retention of handsheet bulk and a consequent improvement in web formation, provided the fibres are of sufficient length.

Kraft handsheet density (or bulk which is the reciprocal of density) and tensile index values over the 500-4000 rev PFI mill refining range for the *E. maidenii* samples from 5- and 6-year-old-trees, are listed in Table 3, together with previously reported data for *E. maidenii* from 8- and 11-year-old-trees, and *E. globulus* from 11-year-old trees. The 5-year *E. maidenii* sheet density, bulk and tensile index values and interrelationships match those of the 8-year *E. maidenii* (Figure 2) and 11-year *E. globulus* pulps (Kibblewhite *et al.* 2000). In contrast, these property relationships are poor for the 6-year *E. maidenii* pulp because of the lower fibre length.

The handsheet properties of bulk, density and tensile index are important determinants of eucalypt kraft pulp quality (Kibblewhite *et al.* 2000). Eucalypt pulps most suitable for papermaking have handsheet densities within the range 600-650 kg/m³, and tensile index values within the range 80-100 N.m/g at 500 PFI mill rev (Table 3). These values are for pulps produced in the laboratory and equate roughly to 560-610 kg/m³ and 34-54 N.m/g for market eucalypt kraft pulps. Hence, the *E. globulus* pulp made from 11-year old trees, and the *E. maidenii* pulp made from the 5- and 8-year-old trees, have fibre properties most suitable for a market kraft end-use. The tensile index and/or sheet density values at 500 rev of the six- and 11-year *E. maidenii* fall outside the ranges for a laboratory pulp and are therefore unsuitable for most eucalypt market pulp end-uses. The 6-year *E. maidenii* pulp has excellent tensile index values, fibre cross-section dimensions and fibre collapse resistance, but with fibre lengths below that required to maintain handsheet bulk.

Table 1: Chip density, and kraft pulp yield and fibre dimensions for *E. maidenii* aged 5- and 6-years; and corresponding data for *E. maidenii* trees aged 8- and 11-years, and *E. globulus* aged 11-years (Kibblewhite *et al.* 2000).

	Chip Density (kg/m ³)	Pulp yield (Kappa 20) (%)	Length (mm)	Perimeter (μm)	Wall area (μm ²)	Wall thickness (μm)	Width/ thickness	Relative number	Sheet density (@ 500 rev) (kg/m ³)
<i>E. maidenii</i> 5 yr	549	53.0	0.84*	38.10	57.22	2.43	1.84	115	613
<i>E. maidenii</i> 6 yr	554	52.4	0.78*	37.53	55.75	2.43	1.87	127	645
<i>E. maidenii</i> 8 yr	569	55.3	0.88	40.7	64	2.59	1.81	98	607
<i>E. maidenii</i> 11 yr	576	55.5	0.94	42.9	73	2.80	1.83	81	566
<i>E. globulus</i> 11 yr	543	54.5	0.85	40.4	62	2.48	1.81	105	629
LSD**	35	1.9	0.04	1.7	6.6	0.29	0.20	20	19

* *E. maidenii* 5-year and 6-year FiberLab3 length values after decrease of 0.06 mm based on calibration curve FS200-FiberLab3 (unreported data).

** Least significant difference (0.05 level) for chip-pile sampling, based on *E. fastigata* (Riddell and Kibblewhite 1999).

Table 3: Handsheet density, bulk and tensile index data (o.d. basis) at four refining levels for *E. maidenii* aged 5- and 6-years; and corresponding data for *E. maidenii* aged 8- and 11-years, and *E. globulus* aged 11-years (Kibblewhite *et al.* 2000).

Sample	PFI mill rev	Apparent density (kg/m ³)	Bulk (cm ³ /g)	Tensile index (N.m/g)
<i>E. maidenii</i> 5-year	500	613	1.63	85.1
	1000	625	1.60	94.2
	2000	Unavailable	Unavailable	Unavailable
	4000	705	1.42	119.0
<i>E. maidenii</i> 6-year	500	645	1.55	86.7
	1000	658	1.52	91.7
	2000	692	1.44	110.8
	4000	738	1.36	119.3
<i>E. maidenii</i> 8-year	500	607	1.65	81
	1000	625	1.60	91
	2000	662	1.51	104
	4000	713	1.40	125
<i>E. maidenii</i> 11-year	500	566	1.77	72
	1000	598	1.67	82
	2000	634	1.58	93
	4000	677	1.48	110
<i>E. globulus</i> 11-year	500	629	1.59	85
	1000	651	1.54	94
	2000	688	1.45	106
	4000	735	1.36	119

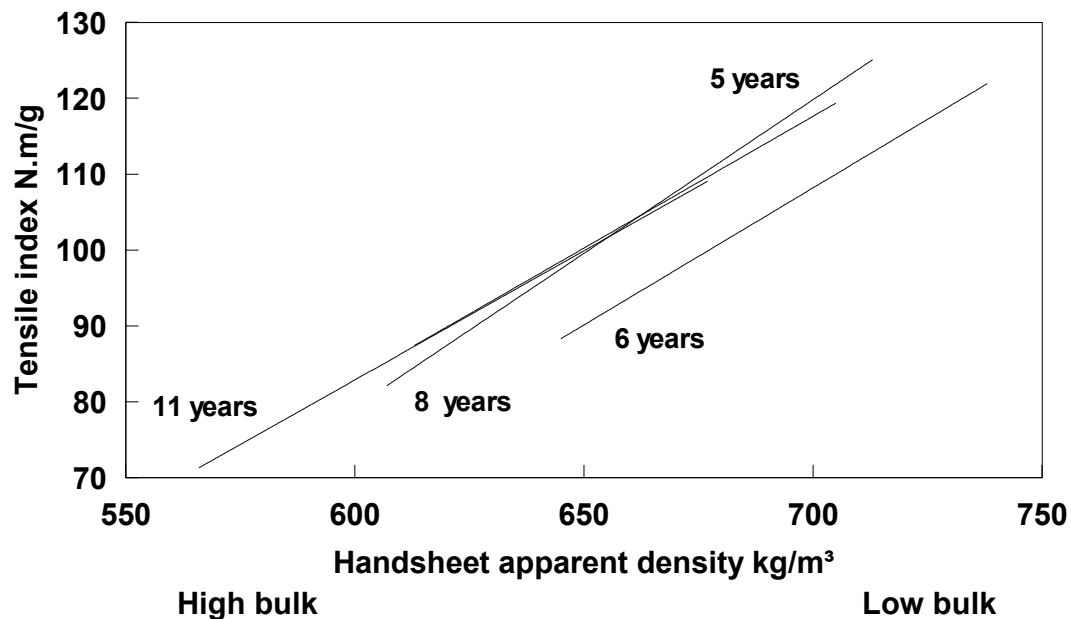


Figure 2: Handsheet tensile index *versus* apparent density regressions based on four PFI mill refining levels for the 5-, 6-, 8- and 11-year *E. maidenii* pulps (Table 3).

The longer fibre length of the pulp from 5-year-old trees from the irrigated pasture site at Waihi versus the 6-year-old trees from the scrub site at Kawerau may be due to a combination of genetic and environmental effects. As the trees sampled from both sites were based on large numbers of parents, though not from the same populations, it seems unlikely that the fibre length difference is primarily genetic. The site at Waihi was a previously topdressed pasture which, after tree planting, had been repeatedly irrigated with sewerage effluent (Gearing *et al.* 2003), in contrast to the untreated site at Kawerau, previously covered by manuka scrub. It seems likely that irrigation plus fertility have given the 5-year-old trees longer fibres than expected for their age. Beadle *et al.* (2001) reported an increase in the fibre length of 6-year-old *E. nitens* in response to irrigation in an experiment in southern Tasmania.

CONCLUSIONS

The fibre and pulp properties of the 5-year-old and 6-year-old *E. maidenii* samples are very similar, except for fibre length. The 5-year sample has the longest fibres (0.84 mm) and has excellent papermaking properties. With high numbers of fibres/mass the 5- and 6-year-old are probably superior to the 8-year *E. maidenii* and 11-year *E. globulus* samples reported previously.

However, the shorter fibre length of the 6-year *E. maidenii* sample (0.78 mm) is below the critical value required to produce the handsheet bulk of a premium kraft pulp.

REFERENCES

1. Beadle, C.L., Banham, P.W., Worledge, D., Russell, S.L., Hetherington, S.J., Honeysett, J.L. and White, D.A.: Effect of irrigation on growth and fibre quality of *Eucalyptus globulus* and *Eucalyptus nitens*. **Appita J.** 54(2):144-147 (2001).
2. Gearing, P.C., Nicholas, I.D., Magesan, G.N., Garrett, L., and Pearce, S. Subsurface drip irrigation of untreated municipal effluent Waihi Beach trial. Proc. Short Rotation Crops for Bioenergy, Field Tour IEA Task 30 Conference Dec 1-5, Tauranga , New Zealand (2003).
3. Kibblewhite, R.P. and Bailey, D.G.: Measurement of fibre cross section dimensions using image processing. **Appita J.** 41(4):297 (1988).
4. Kibblewhite, R.P., Johnson, B.I. and Shelbourne, C.J.A.: Kraft pulp qualities of *Eucalyptus nitens*, *E. globulus* and *E. maidenii*, at ages 8 and 11 years. **New Zealand Journal of Forestry Science** 30(3):447-457(2000).
5. Pettersen, R. and Schwandt, V. Wood sugar analysis by anion chromatography. **Journal of Wood Chemistry and Technology** 11(4): 495-501 (1991).
6. Richardson, J.D., Riddell, M.J.C. and Burrell, P.: Experience with the FiberLab™ v3.0 analyser for measuring fibre cross-section dimensions. Proceedings of the 57th Appita Annual General Conference, Melbourne (2003).
7. Riddell, M.J.C. and Kibblewhite, R.P. Variation in test results for kraft pulp wood chip evaluations. **Appita J.** 52(6): 454-459 (1999).